


EFFECT OF HOT WIRE FILLER METAL ADDITION ON GTAW HEAT INPUT FOR CORROSION RESISTANT OVERLAYS

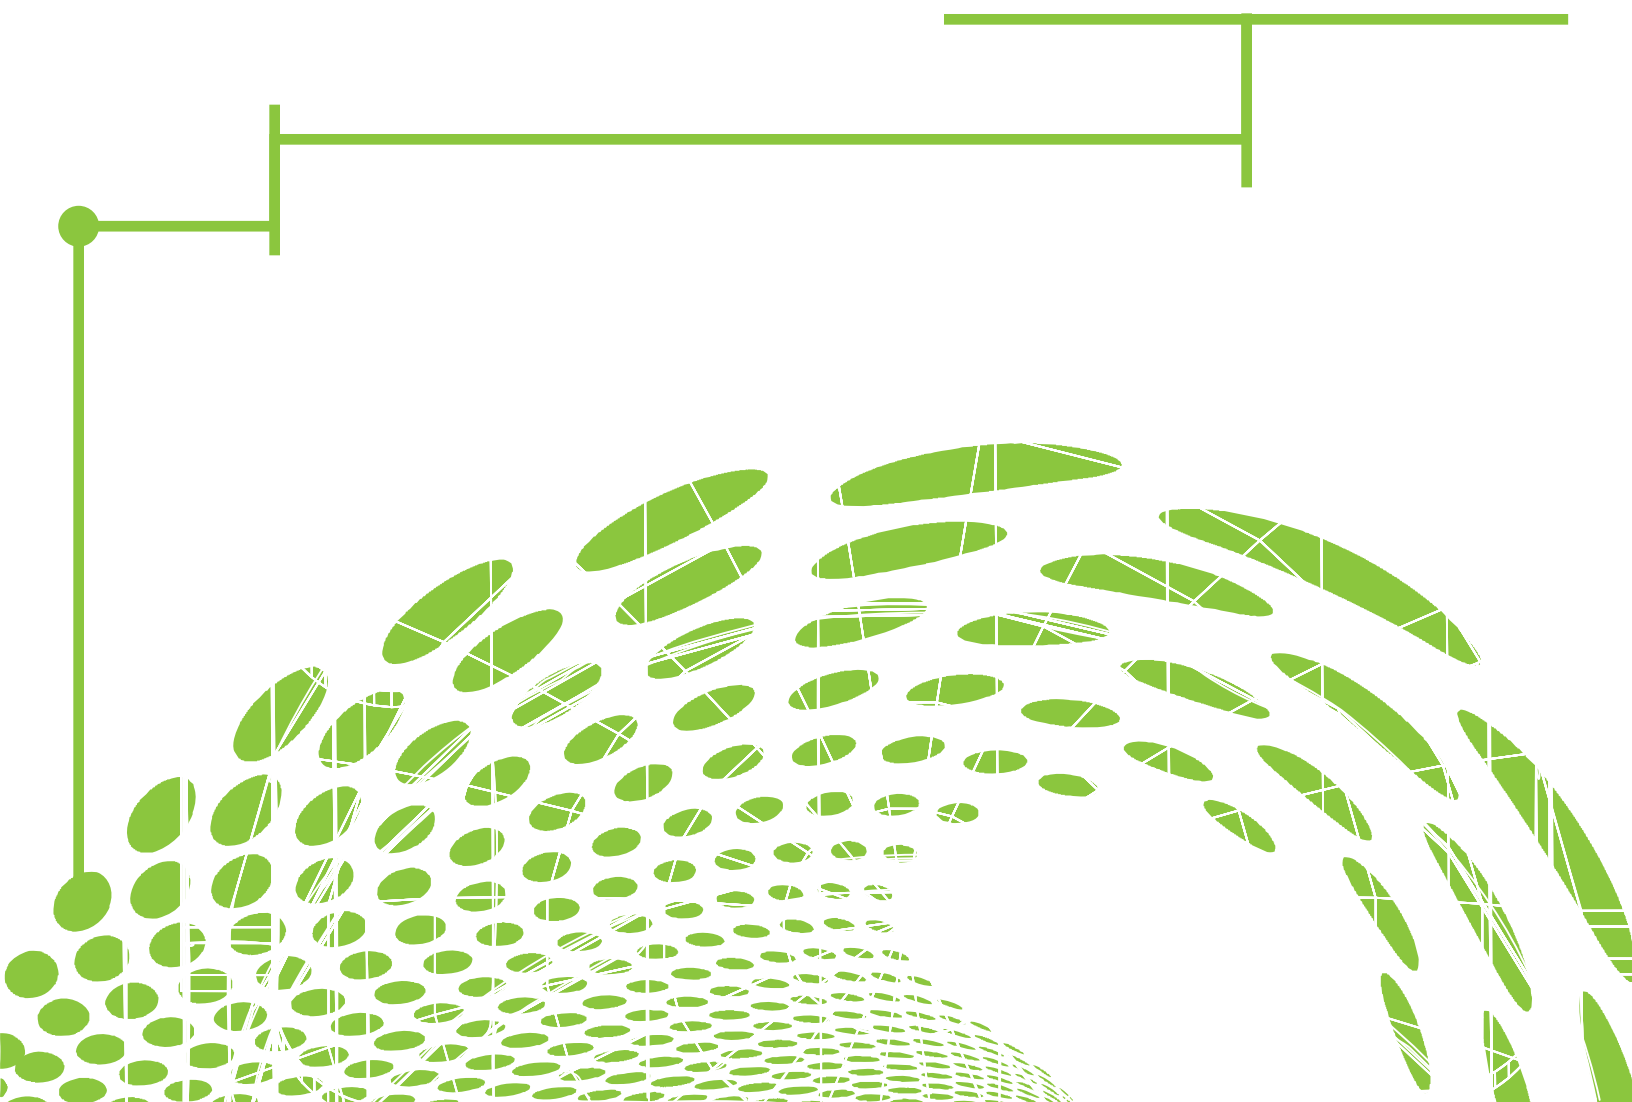

STP-PT-085

Effect of Hot Wire Filler Metal Addition on GTAW Heat Input for Corrosion Resistant Overlays and its Resulting Effect on Heat-affected Zone Hardness and Toughness and Corrosion Resistant Overlay Chemical Composition

Prepared by:

Richard L. Holdren, PE/SWE ARC Specialties Technical Services
David A. Hebble, SWE ARC Specialties Technical Services



Date of Issuance: June 30, 2017

This report was prepared by ASME Standards Technology, LLC (ASME ST-LLC) and sponsored by the American Society of Mechanical Engineers (ASME) Pressure Technology Codes & Standards.

Neither ASME, ASME ST-LLC, the authors, nor others involved in the preparation or review of this report, nor any of their respective employees, members or persons acting on their behalf, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe upon privately owned rights.

Reference herein to any specific commercial product, process or service by trade name, trademark, manufacturer or otherwise does not necessarily constitute or imply its endorsement, recommendation or favoring by ASME ST-LLC or others involved in the preparation or review of this report, or any agency thereof. The views and opinions of the authors, contributors and reviewers of the report expressed herein do not necessarily reflect those of ASME ST-LLC or others involved in the preparation or review of this report, or any agency thereof.

ASME ST-LLC does not take any position with respect to the validity of any patent rights asserted in connection with any items mentioned in this document, and does not undertake to insure anyone utilizing a publication against liability for infringement of any applicable Letters Patent, nor assumes any such liability. Users of a publication are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, is entirely their own responsibility.

Participation by federal agency representative(s) or person(s) affiliated with industry is not to be interpreted as government or industry endorsement of this publication.

ASME is the registered trademark of the American Society of Mechanical Engineers.

No part of this document may be reproduced in any form,
in an electronic retrieval system or otherwise,
without the prior written permission of the publisher.

ASME Standards Technology, LLC
Two Park Avenue, New York, NY 10016-5990

ISBN No. 978-0-7918-7172-0
Copyright © 2017
ASME Standards Technology, LLC
All Rights Reserved

TABLE OF CONTENTS

Foreword.....	iii
1 Background and Introduction.....	1
1.1 Project Objective.....	1
1.2 Materials.....	1
2 Weld Trial Matrix – CRO Welds.....	2
3 Testing Program.....	5
3.1 Hardness Testing.....	5
3.2 Chemical Analysis.....	6
3.3 Deposit Area Measurement.....	6
3.4 CRO Test Results.....	7
4 Summary of CRO Test Results.....	20
5 Groove Weld testing.....	22
5.1 Testing Program.....	23
5.2 Groove Weld Test Results.....	24
6 Summary and Conclusions.....	32
Appendix A: Hardness Mapping of the P-22 As-Welded Samples.....	35

LIST OF FIGURES

Figure 2-1: ARC-HVT set for horizontal welding position.....	3
Figure 2-2: ARC-HVT set for flat welding position.....	3
Figure 3-1: Microhardness test locations for CRO welds.....	5
Figure 3-2: CRO chemical analysis locations for API vs ASME qualification.....	6
Figure 3-3: Image of P22 sample A/B used for weld bead area determination using Jackson Method.....	7
Figure 3-4: Macro sections of P22 CRO welds.....	8
Figure 3-5: Macro sections of 4130 CRO welds.....	9
Figure 3-6: Relationships among HAZ Hardness, Heat Input Rate, and Percent Fe – P22 / As-welded.....	10
Figure 3-7: Relationships among HAZ Hardness, Heat Input Rate, and Percent Fe – P22 / PWHTd.....	11
Figure 3-8: Comparison of as-welded and PWHT HAZ hardnesses for P22 CROs.....	12
Figure 3-9: Relationships among HAZ Hardness, Heat Input Rate, and Percent Fe – 4130 / As-welded.....	13
Figure 3-10: Relationships among HAZ Hardness, Heat Input Rate, and Percent Fe – 4130 / PWHTd.....	14
Figure 3-11: Comparison of as-welded and PWHT HAZ hardnesses for 4130 CROs.....	15
Figure 3-12 HAZ hardnesses versus wire feed speeds and WFS:TS ratios for P22 CROs.....	16
Figure 3-13: HAZ hardnesses versus wire feed speeds and WFS:TS ratios for 4130 CROs.....	17
Figure 3-14: Comparison of heat input rates with wire feed speeds and WFS:TS ratios for P22 and 4130 CRO.....	18
Figure 3-15: Percent Fe versus weld bead area, wire feed speed, and wire feed speed-travel speed ratio – P22.....	19
Figure 3-16: Percent Fe versus weld bead area, wire feed, speed and wire feed speed-travel speed ratio – 4130.....	19
Figure 5-1: Groove joint design.....	22
Figure 5-2: Microhardness test locations for groove welds.....	23
Figure 5-3: Macrosections of P22 groove welds – As-welded.....	24
Figure 5-4: Close-ups of P22 groove welds – As-welded.....	24
Figure 5-5: Macrosections of P22 groove welds – PWHTd.....	24

Figure 5-6: Close-ups of P22 groove welds – PWHTd.....25
Figure 5-7: Macrosections of 4130 groove welds – As-welded25
Figure 5-8: Close-ups of 4130 groove welds – As-welded.....25
Figure 5-9: Macrosections of 4130 groove welds – PWHTd26
Figure 5-10: Close-ups of 4130 groove welds – PWHTd.....26
Figure 5-11: P22 as-welded and PWHTd average breaking energies versus notch location.....27
Figure 5-12: P22 as-welded and PWHTd average breaking energies versus HIR.....28
Figure 5-13: 4130 as-welded and PWHTd average breaking energies versus notch location.....28
Figure 5-14: 4130 as-welded and PWHTd average breaking energies versus HIR.....29
Figure 5-15: P22 groove weld microhardness traverses30
Figure 5-16: 4130 groove weld microhardness traverses30

LIST OF TABLES

Table 2-1: Welding parameters and resulting heat input rates for P22 and 4130 CRO welds.....4
Table 3-1: As-welded P2210
Table 3-2: PWHTd P2211
Table 3-3: As-welded 4130.....13
Table 3-4: PWHTd 4130.....14
Table 5-1: Groove weld parameters.....23
Table 5-2: Impact test results27
Table 5-3: Vickers microhardness test results29

FOREWORD

The purpose of this project is to explore the effects of hot wire filler metal addition with respect to the resulting weld metal and heat-affected zone (HAZ) properties.

Welding procedures for corrosion-resistant overlays (CROs) are heat input limited for the first layer. In applications where NACE International standard NACE MR0175 requirements additionally limit the range of qualified procedures, hot wire filler metal addition is commonly employed to enhance the relatively low deposition rate of the gas tungsten arc welding (GTAW) process. For these applications, typical conditions/requirements include: use of hardenable base metals, maximum iron content at minimum qualified overlay thickness of 5% with Inconel 625 filler metal, and maximum HAZ hardness of 250 HV10. While understood that increasing the heat input will result in a softer HAZ, that increase will also result in greater dilution, negatively affecting the chemical composition of the CRO.

For these applications, the industry requires that the energy supplied to preheat the filler metal (“hot wire”) is included to contribute to the heat input for the process, even though not required by the ASME Boiler and Pressure Vessel Code (BPVC) Section IX. This secondary power is not even limited as an essential variable.

The primary industry impacted by this is the upstream petroleum equipment manufacturers and their suppliers. The economic impact relates to the effect on productivity. If the secondary power being applied to the filler metal does affect the resulting weld properties, then the committee should consider adding qualification restrictions. At this point, it is not clear whether this secondary power has either positive or negative effects.

The authors extend their thanks to various members of the ASME BPVC Section IX Committee for their support of this project. It is hoped that the results generated in this report will benefit all of this code. Thanks are also given to reviewers Ms. Teresa Melfi, Mr. Michael Rice, Mr. Marcello Consonni, Mr. Eugene Woelfel, Mr. Jonathan Lee, Mr. Phillip Van Fosson, Mr. Michael Pischke, and Mr. Arjan Roza for their thoughtful comments and to Mr. Steven Rossi of ASME ST-LLC and Mr. Gerardo Moino of ASME for coordinating various phases of this project.

Established in 1880, the ASME is a professional not-for-profit organization with more than 135,000 members and volunteers promoting the art, science and practice of mechanical and multidisciplinary engineering and allied sciences. ASME develops codes and standards that enhance public safety, and provides lifelong learning and technical exchange opportunities benefiting the engineering and technology community. Visit <https://www.asme.org/> for more information.

ASME ST-LLC is a not-for-profit Limited Liability Company, with ASME as the sole member, formed in 2004 to carry out work related to new and developing technology. The ASME ST-LLC mission includes meeting the needs of industry and government by providing new standards-related products and services, which advance the application of emerging and newly commercialized science and technology, and providing the research and technology development needed to establish and maintain the technical relevance of codes and standards. Visit <http://asmestllc.org/> for more information.

1 BACKGROUND AND INTRODUCTION

Steel piping, valves, blow-out preventers (BOPs), and other processing components require protection from contact with hydrogen sulfide-laden oil or gas. These “sour” products are the current norm for deep wells in the Gulf of Mexico and other areas. Corrosion-resistant alloy overlays are also used in the pressure vessel industry for various applications. Without a protective layer of a corrosion-resistant alloy, catastrophic failures, due to stress-corrosion cracking, will occur. The prominent method for application of this protective layer is to apply a CRO using some welding process. The process most favored is the gas tungsten arc welding process using an energized filler metal feed, commonly referred to as “hot wire” (GTAW-HW). By preheating the filler wire, greater deposition rates can be achieved.

ASME BPVC Section IX does not address the use of hot wire filler metal addition in terms of parameter limits or whether the power is included in the determination of heat input rate (HIR)¹. In upstream (pre-refinery) oil and gas applications, the tendency has been to add this secondary (hot wire) power to the primary (arc) power to calculate HIR; however, there have been questions raised in terms of whether the secondary power actually contributes to the amount of energy being supplied to the base metal or is consumed in the process of preheating the filler metal. This study will attempt to quantify what contribution, if any, is provided by the secondary power to affect the resulting HAZ properties and chemical composition of the CRO.

1.1 Project Objective

The primary objective of this study was to determine if any technical justification exists for consideration of the addition or modification of essential variables to include the secondary power from hot wire additions.

1.2 Materials

While this topic may be of interest in other industries and applications, it is known to be of concern in these upstream oil and gas applications. ARC Specialties is the leading producer of automated welding systems used for applying CROs to a variety of components, with 300+ systems in operation around the world. While several different welding processes are employed in these systems, the vast majority utilize GTAW-HW.

Consequently, the materials chosen for this study will be those most commonly employed for these upstream oil and gas applications. The two base metals most commonly employed are quenched and tempered versions of AISI 4130 and 2¼ Cr – 1 Mo (P-5A, Grade 22). In most cases, the forged versions of these base metals are used; however, this adds significantly to the cost. In the original proposal, Grade 22 was the only material to be included in this study, but there is far more 4130 material used than Grade 22. Consequently, to provide more data, pipe grades of the two materials were used because compositionally the pipe and forging materials are virtually identical. Below are the two base metals to be used for this study, and material certs are attached:

- SA335 Grade P22 – Ht #986957 – $CE_{IHW} = 0.825$; 8.625 inches OD x 0.812 inches wall
- A519 Grade 4130 – Ht #J4038 – $CE_{IHW} = 0.663$; 8.625 inches OD x 1.5 inches wall

The overlay material was Inconel® 625 (SFA5.9, ERNiCrMo-3). The size used was 0.045 inches (1.2 millimeter (mm)) diameter. Lincoln offered to supply the filler metal for this work. The type and classification are shown below and the material cert is attached.

- 0.045 inches [1.2 mm] TECHALLOY 625 33SSP – Ht #QT594

¹ This publication uses the technically-correct term *heat input rate (HIR)* to describe the amount of energy input per unit length of weld. This varies from the terminology, *heat input (HI)*, used in ASME BPVC Section IX; however, for the purposes of this publication, the two terms shall be considered synonymous.